

AD A071 045

NATIONAL BUREAU OF STANDARDS WASHINGTON DC SURFACE S--ETC F/G 7/4
13 C NMR OF CO CHEMISORBED ONTO DISPERSED RHODIUM.(U)

JUN 79 T M DUNCAN, J T YATES, R W VAUGHAN

N00014-79-F-0014

UNCLASSIFIED

TR-14

NI


1 OF 1

AD
A071 045



END
DATE
FILMED

8--79
DDC

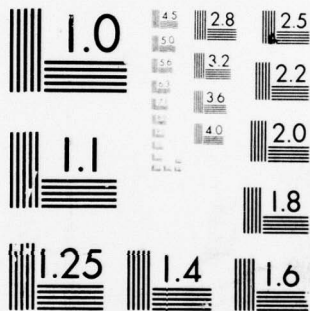

MICROCOPY RESOLUTION TEST CHART
NATIONAL BUREAU OF STANDARDS-1963-A

AD A071045

LEVEL


(15) OFFICE OF NAVAL RESEARCH
Contracts N00014-79-F-0014 and N00014-75-C-0960

N00014-79-F-0014

(9) Technical Report #14

(6) ^{13}C NMR of CO Chemisorbed onto Dispersed Rhodium.

(10) T. M. / Duncan, J. T. / Yates, Jr. * and R. W. / Vaughan**
Division of Chemistry and Chemical Engineering
California Institute of Technology
Pasadena, California 91125

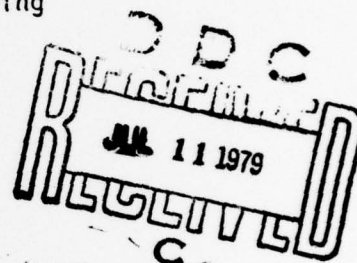

(11) June, 1979

(12) 8p.

(14) TR-14

Reproduction in whole or in part is permitted for
any purpose of the United States Government

DDC FILE COPY

Approved for Public Release; Distribution Unlimited

To be published in the J. Chem. Phys. (Communication)

410 655

29 07 09 200

LB

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER Technical Report No. 14 ✓	2. GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) ¹³ C NMR of CO Chemisorbed onto Dispersed Rhodium	5. TYPE OF REPORT & PERIOD COVERED	
		6. PERFORMING ORG. REPORT NUMBER
7. AUTHOR(s) T. M. Duncan, J. T. Yates, Jr. and R. W. Vaughan	8. CONTRACT OR GRANT NUMBER(s) N00014-79-F-0014 ✓ N00014-75-C-0960	
9. PERFORMING ORGANIZATION NAME AND ADDRESS California Institute of Technology, Div. of Chem. and Chem. Engr., Pasadena, CA and Surface Science Division, National Bureau of Standards, Wash., DC	10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS	
11. CONTROLLING OFFICE NAME AND ADDRESS Office of Naval Research Chemistry Program Office Arlington, VA 22217	12. REPORT DATE June, 1979	13. NUMBER OF PAGES
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)	15. SECURITY CLASS. (of this report) Unclassified	
	15a. DECLASSIFICATION/DOWNGRADING SCHEDULE	
16. DISTRIBUTION STATEMENT (of this Report) Approved for Public Release; Distribution Unlimited.		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES Preprint; to be published in the J. Chem. Phys. (Communication)		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Chemisorption, nuclear magnetic resonance, ¹³ C, carbon monoxide, rhodium, catalysis.		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) <div style="display: flex; align-items: center;"> <div style="margin-right: 10px;">↙</div> <div> ¹³C NMR spectrum of carbon monoxide chemisorbed on supported rhodium has been studied. Temperature dependent lineshape changes have been observed suggesting that anisotropic carbon monoxide motions occur in the chemisorbed layer. </div> </div> <div style="text-align: center; margin-top: 10px;">↘</div>		

DD FORM 1 JAN 73 1473

EDITION OF 1 NOV 65 IS OBSOLETE
S/N 0102-014-6601UNCLASSIFIED
SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

[Empty rectangular box for content]

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

^{13}C NMR of CO Chemisorbed onto Dispersed Rhodium #

T. M. Duncan, J. T. Yates, Jr.* and R. W. Vaughan**

Division of Chemistry and Chemical Engineering

California Institute of Technology

Pasadena, California 91125

*Work performed while a Sherman Fairchild Distinguished Scholar at Caltech;
permanent address: Surface Science Division, National Bureau of Standards,
Washington, D.C. 20234

#Supported in part by the Office of Naval Research under Contracts N00014-75-C-960
and N00014-77-F-0008

**Deceased

Accession For		
NIS GR&I	<input checked="" type="checkbox"/>	<input type="checkbox"/>
DEC TAB	<input type="checkbox"/>	<input type="checkbox"/>
Unannounced		
Justification		
By		
Distribution		
Available in		
Available/or		
Dist special		
Dist	A	

The chemisorption of CO on transition metals has been extensively studied in attempts to characterize the adsorbed state of the molecule¹⁻⁵. We wish to report here the first observation of a molecule chemisorbed on a dispersed metal catalyst by ^{13}C nuclear magnetic resonance (NMR). The preliminary spectra reported indicate that the adsorbed CO is undergoing anisotropic, or "fluxional," motion on the surface and strongly imply the presence of a species not observed by infrared techniques. To date, evidence for the surface intermediates for the catalytic methanation reaction of CO and H_2 over dispersed metal catalysts has been based on infrared studies⁶. Thus, the presence of a previously unobserved surface species is potentially important in understanding the reaction mechanism.

The sample was contained in a specially constructed infrared/NMR cell where both infrared and NMR measurements could be made. The infrared cell, a stainless steel body with single crystal CaF_2 windows, and the bakeable, all-metal 10^{-8} Torr vacuum system have been previously described¹. The NMR measurements were made at 14.7 MHz in a 10 mm single-resonance probe using a previously described spectrometer⁷. A 10 mm pyrex tube fused to a copper tube and then welded to a $\frac{1}{8}$ inch stainless steel port of the infrared cell¹ served as the NMR sample holder. Since the low signal level of the NMR signals required signal averaging, an alternative pulse sequence, $90^\circ/180^\circ-\tau-90^\circ$, was used with free-induction decays taken after each 90° pulse and alternately added and subtracted to eliminate instrumental artifacts. Approximately 400,000 such transients were accumulated for the room-temperature spectra and 100,000 for the lower temperature spectra. Transients were accumulated with $\tau = 500$ microseconds at intervals of 0.40 seconds to optimize the signal-to-noise.

The 2.2% Rh on Al_2O_3 sample was prepared as previously described^{1,5}, but with the addition of 100 ppm of Fe to the sample. The 2.2% Rh/ Al_2O_3 sample

was then reduced in H_2 at $150^\circ C$ and degassed as previously described¹ and then exposed to 50 torr of 90% ^{13}C -enriched CO at room temperature. An infrared spectrum taken between 4000 and 1200 cm^{-1} confirmed that the surface was free of impurities observable by IR prior to adsorption. The infrared spectrum taken after adsorption was identical to the previously reported spectra taken at saturation coverages (see Figure 5d, reference 1). The corresponding ^{13}C NMR spectrum taken at 300 K is shown in Figure 1a. The CO gas pressure was reduced to 0.02 torr to prevent any extraneous signal from CO condensed on the alumina, and the ^{13}C NMR spectrum was taken again at 80 K and is illustrated in Figure 1b. Finally, the solid state ^{13}C spectra of a model compound, $Rh_2Cl_2(CO)_4$ was taken at room temperature (328 transients) and is shown for comparison in Figure 1c. The area of the ^{13}C spectra indicates that there is ~0.9 CO molecule adsorbed for each Rh atom, and this is consistent with an extrapolation of previously obtained adsorption isotherms at lower coverage.¹

The center of mass, or isotropic chemical shift, of each spectrum is located near -191 ppm relative to tetramethylsilane (note σ values⁸, not δ values are reported here). The constant center of mass together with a temperature-dependent lineshape that approaches that of the model compound at the lowest temperatures studied indicates that an activated anisotropic reorientational motion of the CO molecule on the surface is responsible for the partial collapse observed in the spectra of the surface-adsorbed CO. It is possible to rule out an activated exchange between the surface-adsorbed and gas phase carbon monoxide since the spectrum did not broaden after the CO gas pressure was reduced by 8 orders of magnitude. Fluxional, or ligand, exchange processes have been observed widely in organometallic molecules⁹ and could be responsible for the observed motional averaging, as could a restricted diffusion over a small metal particle. Since the anisotropy of the ^{13}C chemical shift tensor of the

carbonyl ligand is very large, ~ 400 ppm, it overlaps the spectra of other possible surface species and a clean separation of such spectra will require the application of more complex NMR techniques including the use of magic-angle sample spinning¹⁰. However, a simple observation of the lineshape changes as a function of surface treatment is already furnishing new information, and possibly most important, evidence for the existence of a previously unobserved species in high concentration on the surface. For example, previous infrared studies^{1,5} have shown that the CO is slowly desorbed from the Rh sites at 300 K. By constantly evacuating with an ion pump for two months, the equilibrium pressure of the sample was reduced to 3×10^{-7} torr. The infrared signal decreased uniformly to 20% of its original area (for example, see Figure 4, reference 1). However, the ^{13}C NMR line retained 85% of its original area. Upon redosing to 50 torr of CO the infrared spectrum returns to 90% of its original intensity and the NMR spectrum returns completely. A naive argument assuming a concentration-independent extinction coefficient for the infrared spectra would suggest that only 20% of the surface species are observed with infrared techniques. Further experimental work confirms that the NMR techniques are observing other species not revealed by the infrared techniques; for example, heating the samples to 423 K for three hours in the presence of 20 torr of CO results in a new sharp feature at $\sigma \sim -176$ ppm in the NMR spectrum and increases the ^{13}C spectrum intensity by 30%, while the infrared spectrum exhibits a depletion of the doublet bond of the $\text{Rh}(\text{CO})_2$ feature. Yet, isotopic exchange experiments (^{13}CO - ^{12}CO) performed at room temperature demonstrate the rapid and complete exchange of all observed surface species for both the NMR and infrared spectra.

In summary, we have reported what we believe to be the first ^{13}C NMR spectra of molecules chemisorbed to a dispersed metal catalyst. We have demonstrated that even these preliminary spectra contain useful information for characterization of the surface species.

References

1. J. T. Yates, Jr., T. M. Duncan, S. D. Worley, and R. W. Vaughan, J. Chem. Phys. 70, 1219 (1979).
2. M. Primet, J. Chem. Soc. Far. Trans. I, 74, 2570 (1978).
3. D. J. C. Yates, L. L. Murrell, E. B. Prestridge, J. Catalysis 57, 41 (1979).
4. R. M. Kroeker, W. C. Kaska, P. K. Hansma, J. Catalysis 57, 72 (1979).
5. A. C. Yang and C. N. Garland, J. Phys. Chem. 61, 1504 (1957).
6. G. A. Mills and F. W. Steffgan, Catal. Rev.-Sci. Eng. 8, 159 (1973);
M. A. Vannice, Catal. Rev.-Sci. Eng. 14, 153 (1976).
7. R. W. Vaughan, D. D. Elleman, L. M. Stacey, W-K. Rhim, and J. W. Lee, Rev. Sci. Instrum. 43, 1356 (1972).
8. M. Mehring, NMR, Basic Principles and Progress, 11 (1976).
9. J. Evans, Adv. Organometallic Chem. 16, 319 (1977).
10. J. Schaefer and E. U. Stejskal, J. Am. Chem. Soc. 98, 1031 (1976).

Figure Caption

Figure 1. ^{13}C NMR spectra of: (i) a 2.2% Rh/ Al_2O_3 sample saturated with 50 torr of ^{13}CO at 300 K; (ii) the same sample, but pumped down to .02 torr ^{13}CO , and cooled to 80 K; and (iii) a solid compound, $\text{Rh}_2\text{Cl}_2(\text{CO})_4$, at 300 K (enriched to 20% ^{13}C).

